

CO₂ Laser Effects on Shear Bond Strength of Orthodontic Brackets and Enamel Demineralization

Nasrin Farhadian^a, Amirfarhang Miresmaeili^a, Loghman Rezaei Soufi, Fahimeh Baghaei^b, Ehsan Shahvali^c

Abstract

Aim: of this in vitro study was to evaluate the effects of Co₂ laser irradiation on demineralization adjacent to orthodontic brackets and their shear bond strength in human premolar teeth. Enamel demineralization adjacent to orthodontic brackets is a major problem that requires new professional method independent to patient cooperation.

Materials and methods: Sixty human premolars were randomly divided to two groups (n=30). Group1, enamel surface irradiated with Co₂ laser. Group2 without any enamel surface treatment. In both groups, a bracket at buccal surface was bonded with Transbond XT and cured with conventional light cure. Demineralization in all sample induced with artificial caries solutions. A universal testing machine was used to determine shear bond strengths. The teeth were sectioned bucco-lingually and were evaluated under polarized light microscope. Average lesion depths were calculated from three depth measurements. The Two independent sample T- tests were used to compare the study type group in detail.

Results: The mean of shear bond strengths in the group1 and 2 were 13.90 ± 5.01 and 15.84 ± 3.68 Mpa respectively, but not statistically significant ($P=0.102$). The mean lesion depth in group1 and 2 was 72.29 ± 58.09 μm and 120.01 ± 76.49 μm respectively, which was significant ($P=0.018$).

Conclusion: Co₂ laser irradiation can reduce enamel demineralization while not affecting the shear bond strengths significantly.

Keywords: CO₂ laser, Shear bond strength, Enamel demineralization

(Received July 2011; Revised and accepted Oct 2011)

Enamel decalcification with white spot formation on buccal surfaces of teeth adjacent to orthodontic brackets is a relatively common side effect of fixed orthodontic appliances.¹⁻³

^a Associated Professor, Hamadan Dental Faculty, Department of Orthodontics

Hamadan Dental Faculty, Department of Orthodontics,

^b Assistant Professor, Hamadan Dental Faculty, Department of Restorative Dentistry

^c Postgraduate Student, Hamadan Dental Faculty, Department of Orthodontic

These appliances make conventional plaque removal more difficult, thus increasing the risk of decalcification on surfaces that normally show a low prevalence of dental caries.⁴ These early carious lesions can be seen as early as 4 weeks after band or bracket placement.⁴⁻⁷ The prevalence of white spot lesions in orthodontic patients has been reported between 2% and 96%.^{1, 8-10} These lesions can occur on all teeth but are most frequently seen on the facial surfaces of maxillary lateral incisors, mandibular canines, and first premolars in the cervical and middle thirds of the teeth.^{3, 11} These

lesions compromise the esthetic results at the end of orthodontic treatment.¹²

Several methods for prevention of this lesions may include: good oral hygiene, nutritional counseling, and treatment with topical fluoride¹³, enamel sealants, modified appliance designs^{4, 14} and laser therapy around the bracket¹⁵. Most of these methods, however, rely on patient compliance, which is unreliable, and could be seen effective only in 13% of orthodontic patients. In this way, compliance-free methods must be developed for more efficient patient care.¹⁶ It was reported that CO₂ laser irradiation can decrease enamel decalcification more than 98%.¹⁷ Although CO₂ laser have not been applied for composite curing, it may probably affect the bond strength, via etching effect on enamel surfaces¹⁸ and these lased surfaces may have superior bond strength than acid-etched enamel ones.¹⁹

Present study evaluates the combination effects of CO₂ laser on enamel demineralization and shear bond strength of orthodontic brackets.

Materials and methods

Sample size was determined based on following formula:

$$\frac{(Z_{1-\alpha/2} + Z_{1-\beta})(\sigma_1^2 + \sigma_2^2)}{(\mu_1 - \mu_2)^2} = \frac{(1.96 + 1.28)(9.3^2 + 8.7^2)}{(15.93 - 6.45)^2} \approx 20$$

In which μ_i and σ_i ($i=1,2$) were obtained from previous study.¹⁵ In this study, the type I error (α) was less than 0.05. So a minimum of 20 subjects in each group was adequate. Teeth with enamel cracks, visible white spots or other stains were excluded. For compensating the probable sample loss sixty intact human premolars immediately after extraction were placed in a solution of 10% formalin. Visible soft tissue removed

with a razor blade, and then the teeth were cleansed and polished with non fluoridated pumice and prophylactic rubber cups. Root of teeth was mounted in cold-cure acrylic resin and then teeth were randomly assigned to the following equal groups: Group 1, enamel surface was exposed to CO₂ laser unit, Smart US-20 D (Deka, Calenzano, Italy). Water used as coolant during lasing process. The unit was set up on level 2 and pulse mode with following parameters: wave length 10.6 μ m, pulse repetition Rate 20HZ, 1 milliseconds per pulse and output power of 1 J. We irradiated brackets position area, a surface about 7 mm by 7mm. The focal spot of the laser was 0.2 mm in diameter. The irradiation was carried out in swabbing motion and precisely irradiated this area. Group 2, enamel surface had not received any laser irradiation. Brackets were bonded to all samples as follows: the buccal surfaces were acid etched for 15 seconds with 37% phosphoric acid, rinsed with water for 30 seconds and dried with an oil free air stream for 20 seconds, giving the enamel a chalky appearance. All brackets (S.S Standard 018 Slot, Dentarum, Germany) were bonded with Transbond XT (3M/ Unitek, Monrovia, California), according to the manufacturer's instruction, using a total 40 seconds (10 seconds from each side of the bracket) conventional light (Optilux 501, Kerr, Orange, Calif, USA) with approximate power of 820mW/cm². Then, all teeth were painted with a thin coat of acid resistance varnish covering all surfaces of the teeth except the buccal surface. The teeth were immersed in a standard tenCate demineralizing solution, (consisting of 2.20 mmol/L calcium, 2.20 mmol/L phosphate, 0.05 mol/L acetic acid, and 0.025 ppm fluoride) at room temperature. After a 10 days exposure to the artificial caries solution, the presence or absence of demineralization were judged by visual inspection of the teeth. The

appearance of frosty white enamel when dried was assigned as the presence of demineralization. Tensile debonding forces were applied at 0.5 mm/second on the testing machine (SANTAM, STM-20, Tehran, Iran) with wire loop occluso-gingivally. Shear bond strength values were calculated based on the peak load at failure divided by the bracket surface area. The mean bond strength values for two studied groups was compared using two independent sample t-test.

Then bracket bases and the enamel surfaces were examined with a stereomicroscope at 10 times magnification to evaluate the amount of adhesive remaining on the teeth. The adhesive remnant index (ARI) was used to assess the quantity of adhesive remaining on the enamel surface. The ARI scores ranged from 0 to 3 according to Årtun.²¹ For comparing the two groups Mann whitney U-test was used.

Root of teeth cut 2 mm apically from cemento-enamel junction. Two cut approximately 2mm apart in buccolingual direction placed on each tooth at the middle of the crown with a water-cooled diamond disk along the long axis of the tooth by a handpiece. Then the thickness of sections reduced to 90-100 micro meters with progressively finer grades of silica carbide grinding paper then the sections were imbibed with water (refractive index 1.33) for evaluation under polarized light microscope (LX400, Labo America, Fremont, USA) (Fig 1 a,b) with 10 x magnification.

A trained operator in blind situation measured the lesion depth 1mm far from cervical of bracket site at the 3 level as shown in schematic figure (Fig 2).

The average of three representative measurements from the surface in 3 zone (coronal, middle, gingival) to the depth of the lesion was calculated. Measuring repeated after 10 day by the same operator. Intra-class correlation was calculated for random error. Data analysis was performed using SPSS 16.0. ARI and shear bond strength was compared using Spearman's Correlation Coefficient test.

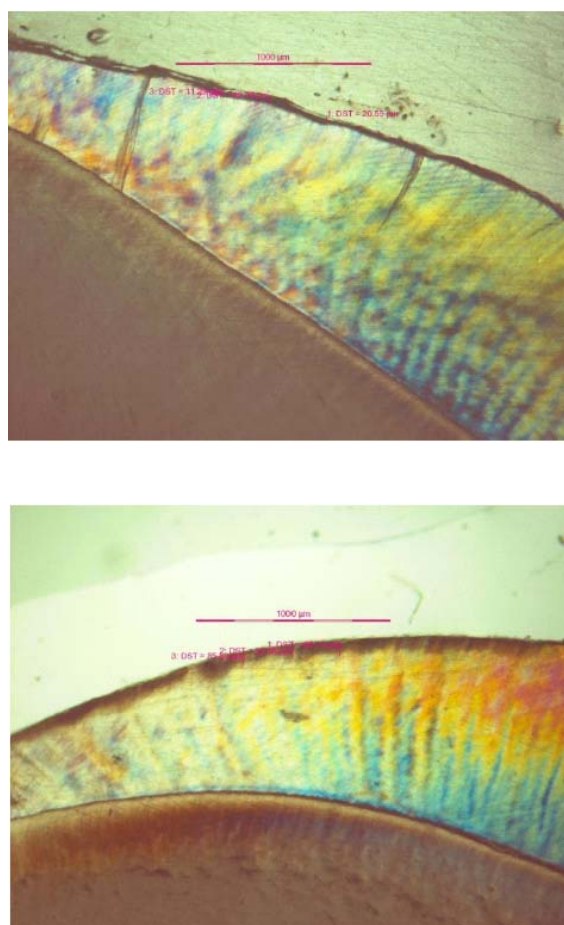


Figure 1: Polarized light micrograph of demineralized enamel lesion in A; laser group and B; control group

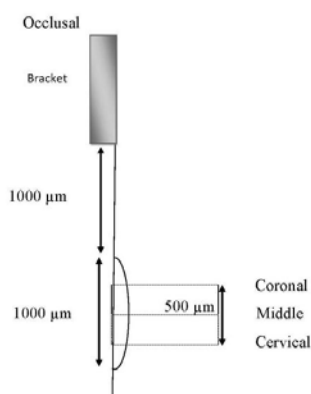


Figure 2: The schematic figure that showed a standardized area for measurements in each specimen

Result

At the end of study 7 teeth in control and 5 ones in laser group were lost. The shear bond strength and demineralization depth were normally distributed according to the Kolmogorov-Smirnov test. Mean shear bond strength in control and laser group was 15.29 ± 3.56 Mpa, 13.41 ± 4.83 MPa respectively. Student T-test analysis showed that there is no significant difference in shear bond strength between two groups ($P=0.102$) (Table 1).

Mann-Whitney U Test showed significant differences in ARI between two groups ($P=0.001$) Mean ranks in group1 and 2 was 0.96 and 1.79 respectively. (Table 2). Spearman correlation coefficient ($r=0.2$) didn't show any significant correlation between ARI and shear bond strength ($P=0.133$).

Mean lesion depth in control and laser groups were 120.01 ± 76.49 μm and 72.29 ± 58.09 μm respectively. Independent Samples T-test showed significant differences between two groups ($P=0.018$) (Table 3). Intra-class Correlation Coefficient was equal to 0.97.

Discussion

The aim of this study was to evaluate the effects of CO₂ laser on enamel demineralization and shear bond strength of orthodontic brackets. According to previous studies CO₂ laser with 10.6 μm wavelength that is commercially available in medical field was selected.²² Present study showed an approximately 42% reduction in demineralization depth in laser group. Kantorowitz et al. with the same wavelength CO₂ laser reported 48% reduction in demineralization.²³

Table 1: Shear Bond Strength in laser(1) and control(2) group

	Group	N	Mean	Std. Deviation	Std. Error Mean	P.Value
<i>Shear bond strength</i>	1	28	13.419	4.837	.914	0.102
	2	29	15.297	3.560	.661	

Table 2: ARI scores in laser(1) and control(2) group

P.Value	Mean Rank		ARI Score		N	Group	
0.001	3		2	1	0		
	.96	1	4	16	7	28	1
	1.79	7	11	9	2	29	2

Table 3: Depth of demineralized lesion in μm

	Group	N	Mean	SD	SE. Mean	P.Value
Mean lesion Depth	1	25	72.296	58.099	11.619	0.018
	2	23	120.011	76.494	15.950	

According to Hsu et al. in a pilot study 17, if the energy density of CO₂ laser irradiation on enamel be more than 3 J/cm², crater formation, surface melting and surface flaking will be observed. Also it is reported if the temperature reaches to 400 °C the majority of enamel structures became positively birefringent.^{25, 26} In present study, laser parameters were selected in such a way to minimize the adverse effects of CO₂ laser on teeth (preventing pulp temperature increase, crater formation and enamel flaking).¹⁷ As sections in the laser group showed relatively negative birefringence, it seems that the laser-induced surface temperature did not reach 400°C. Fowler et al. and Holcomb et al., reported that enamel proteins decompose between 300 - 400°C and reduction of enamel demineralization are maximum in this range.²⁷⁻²⁸ The exact effect of CO₂ laser on enamel that results in enamel resistance to demineralization still not clearly understood.

Several mechanisms proposed for this effect including:

the combination of reduced enamel permeability with a reduced solubility with melting, fusion and sealing the enamel surface²⁹⁻³⁰, ultra-structural crystallographic effects such as different shape and larger size of apatite crystals, and loss of prismatic structure³¹. Also conversion of acid phosphate to pyrophosphate 28 and partial decomposition of the organic matrix 17 are responsible for producing of acid resistant layer on enamel surface.³²

Considering the effect of laser on enamel surface and structural changes that influence the acid resistance of enamel may possibly affect the shear bond strength of orthodontic brackets. In present study, shear bond strength of two groups had no statistically significant differences, so it could be used successfully for orthodontic clinical purposes.³³ Several studies reported use of CO₂ laser as enamel etchant. CO₂ laser induced physical changes such as melting,

recrystallization, formation of numerous porosity and small bubbles like lesions, which is similar to Type III pattern of etching with phosphoric acid. This increased level of roughness and irregularities, provides micro-mechanical retention for the adhesive materials.³⁴⁻³⁵ In spite of the surface roughness, some researchers reported that shear bond strength in laser etched samples was lower than acid etched samples³⁶⁻³⁷ and some others reported comparable bond strength.³⁸ Walsh and colleagues reported greater shear bond strength than acid etched with this laser parameter (power density 2380 W/cm², energy density 23.8 J/cm²) but with this power the adverse effects on enamel could be expected.^{17, 39}

In present study, according to the selected laser parameters (less than 3J/cm²), photothermal phenomena seems to be occurred and this changes merely reduces the solubility of enamel and enamel demineralization process and has not the negative impact on acid etching process and resulted bond strength.

ARI scores characterize the type of bond failure. High ARI scores in control group show that failure occurs at adhesive/bracket interface 40 and more adhesive remained on enamel surface relative to laser group. In present study in spite of significant difference in ARI between two groups there is no correlation with shear bond strength value. It may be the advantage of laser that permits orthodontist to clean remained adhesives at debonding stage more easily.

Conclusion

Apply CO₂ laser on enamel surface considerably reduces enamel demineralization and it didn't show negative impact on the shear bond strength of orthodontic brackets. In spite of its favorable

effect on enamel, cost of this method is a limiting factor to make it popular.

References

- 1-Gorelick L, Geiger AM, Gwinnett AJ. Incidence of white spot formation after bonding and banding. *Am J Orthod* 1982;81:93-8.
- 2- Wisth PJ, Nord A. Caries experience in orthodontically treated individuals. *Angle Orthod* 1977;47: 59-64.
- 3- Årtun J, Brobakken BO. Prevalence of carious white spots after orthodontic treatment with multibonded appliances. *Eur J Orthod* 1986; 8:229-34.
- 4- Øgaard B, Rolla G, Arends J. Orthodontic appliances and enamel demineralization. Part 1. Lesion development. *Am J Orthod Dentofacial Orthop* 1988; 94:68-73.
- 5-Glatz EGM, Featherstone JDB. Demineralization related to orthodontic bands and brackets. *Am J Orthod* 1985;87:87.
- 6-Diedrich P. Enamel alterations from bracket bonding and debonding: a study with the SEM. *Am J Orthod* 1981;79:500-22.
- 7-O'Reilly MM, Featherstone JD. Demineralization and remineralization around orthodontic appliances: an in vivo study. *Am J Orthod Dentofacial Orthop* 1987; 92:33-40.
- 8-Mizrahi E (1982) Enamel demineralization following orthodontic treatment. *Am J Orthod* 1982;82:62-7.
- 9-Ogaard B, Rolla G, Arends J, Ten Cate JM. Orthodontic appliances and enamel demineralization. Part 2. Prevention and treatment of lesions. *Am J Orthod Dentofacial Orthop* 1988; 94:123-8.
- 10-Mitchell L. Decalcification during orthodontic treatment with fixed appliances—an overview. *Br J Orthod* 1992;19:199-205.

- 11- Geiger AM, Gorelick L, Gwinnett AJ, Griswold PG. The effect of a fluoride program on white spot formation during orthodontic treatment. *Am J Orthod Dentofacial Orthop* 1988;93:29-37.
- 12- Farrow ML, Newman SM, Oesterle LJ, Shellhardt WC. Filled and unfilled restorative materials to reduce enamel decalcification during fixed-appliance orthodontic treatment. *Am J Orthod Dentofacial Orthop* 2007;132:578.e1-6.
- 13-Farhadian N, Miresmaeili A, Eslami B, Mehrabi S. Effect of fluoride varnish on enamel remineralization around brackets: An in-vivo study. *Am J Orthod Dentofacial Orthop* 2008;133:S95-8.
- 14-Joseph VP, Rossouw PE, Basson NJ. Some —sealants□ seal: a scanning electron microscopy (SEM) investigation. *Am J Orthod Dentofacial Orthop* 1994; 105:362-8.
- 15-Anderson AM, Kao E, Gladwin M, Benli O, Ngan P. The effects of argon laser irradiation on enamel decalcification: an in vivo study. *Am J Orthod Dentofacial Orthop* 2002;122: 251-9.
- 16-Todd MA, Staley RN, Kanellis MJ, Donly KJ, Wefel JS. Effect of fluoride varnish on remineralization adjacent to orthodontic brackets. *Am J Orthod Dentofacial Orthop* 1999;116:159-67.
- 17-Hsu CY, Jordan TH, Dederich DN, Wefel JS. Effects of Low-energy CO₂ Laser Irradiation and the Organic Matrix on Inhibition of Enamel Demineralization. *J Dent Res* 2000; 79: 1725-30.
- 18-Roberson TM, Heymann HO, Swift EJ. Art and science of operative dentistry. 5th ed, Mosby, 2006; St. Louis, Missouri, 346.
- 19-Lin S, Caputo AA, Eversole LR, Rizoio I. Topographical characteristics and shear bond strength of tooth surfaces cut with a laser-powered hydrokinetic system. *J Prosthet Dent* 1999;82:451-5.
- 20-Buren JL, Staley RN, Wefel J, Qian F. Inhibition of enamel demineralization by an enamel sealant, Pro Seal: An in-vitro study. *Am J Orthod Dentofacial Orthop* 2008; 133:S88-94.
- 21- Årtun J, Bergland S. Clinical trials with crystal growth conditioning as an alternative to acid-etch enamel pretreatment. *Am J Orthod* 1984; 85:333-40.
- 22- Rodrigues LK, dos Santos MN, Pereira D, Assaf AV, Pardi V. Carbon dioxide laser in dental caries prevention. *Journal of Dentistry* 2004; 32: 531–40.
- 23- Kantorowitz Z, Featherstone JDB, Fried D. Caries prevention by CO₂ laser treatment: dependency on the number of pulses used. *Journal of the American Dental Association* 1998;129:585-91.
- 24- Featherstone JDB, Barrett-Vespone NA, Fried D, Kantorowitz Z, Seka W. CO₂ laser inhibitor of artificial caries like lesion progression in dental enamel. *Journal of Dental Research* 1998;77:1397-1403.
- 25-Sato K. Relation between acid dissolution and histological alteration of heated tooth enamel. *Caries Res* 1983; 17:490-5.
- 26-Oho T, Morioka T. A possible mechanism of acquired acid resistance of human dental enamel by laser irradiation. *Caries Res* 1990;24:86-92.
- 27-Fowler BO, Kuroda S. Changes in heated and in laser-irradiated human tooth enamel and their probable effects on solubility. *Calcif Tissue Int* 1986; 38:197-208.
- 28-Holcomb DW, Young RA. Thermal decomposition of human tooth enamel. *Calcif Tissue Int* 1980;31:189-201.
- 29-Nelson DGA, Shariati M, Glana R, Shields CP, Featherstone JDB. Effect of pulsed low energy infrared laser irradiation on artificial caries-like lesion formation. *Caries Research* 1986;20:289-99.
- 30-Nelson DGA, Wefel JS, Jongebloed WL, Featherstone JDB. Morphology, histology and crystallography of human dental enamel treated with pulsed low-energy infrared laser irradiation. *Caries Research* 1987;21:411-26.

- 31- Stern RH, Vahl J, Sognnaes RF. Lased enamel: ultrastructural observations of pulsed carbon dioxide laser effects. *Journal of Dental Research* 1972;51:455-60.
- 32-Pogrel MA, Muff DF, Marshall GW. Structural change in dental enamel induced by high energy continuous wave carbon dioxide laser. *Lasers Surg Med* 1993;13:89-96.
- 33-Reynolds IR. A review of direct orthodontic bonding. *Br J Orthod* 1975;2:71-8.
- 34- MacDonald R, Zakariasen KL, Peters J, Best S. Comparison of lased and acid etched enamel using scanning electron microscopy. *J Dent Res* 1990;69:174. (Abstract)
- 35-Silverstone LM, Saxton CA, Dogon IL, Fejerskov O. Variations in the pattern of etching of human dental enamel examined by scanning electron microscopy. *Caries Res* 1975; 9:373-87.
- 36-MacDonald RM, Lobb W, Boran T, Nichols M. The bonding/failure characteristics of orthodontic brackets using laser etching. *J Dent Res* 1994; 73:198. (Abstract)
- 37-Poulsen J, DhuruV, Ferguson D, Kittleson R, Stenger J. Orthodontic bond strength after etching enamel with CO₂ laser. *J Dent Res* 1993; 72:176. (Abstract)
- 38-Liberman R, Segal TH, Nordenberg D, Serebro LI. Adhesion of composite materials to enamel: Comparison between the use of acid and lasing as pretreatment. *Lasers Surg Med* 1984;4:323-7.
- 39-Walsh LJ, Abood D, Brockhurst PJ. Bonding of resin composite to carbon dioxide laser-modified human enamel. *Dent Mater* 1994;10:162-6.
- 40-Blankenau RJ, Powell GL, Kelsey WP, Barkmeier WW. Post polymerization strength values of an argon laser cured resin. *Lasers Surg Med* 1991;11:471-4.